

The Overlooked Key Factors for Accurate Determination of Polymer Triboelectric Series

Journal:	SCIENCE CHINA Materials
Manuscript ID	SCMs-2025-0699.R1
Manuscript Type:	Perspective
Date Submitted by the Author:	09-Jun-2025
Complete List of Authors:	Meng, Hongyu; Institute of Nanoenergy and Nanosystems Chinese Academy of Sciences Gai, Yansong; Institute of Nanoenergy and Nanosystems Chinese Academy of Sciences, gaiyansong@163.com Bai, Yuan; Institute of Nanoenergy and Nanosystems Chinese Academy of Sciences Yu, Qiao; Institute of Nanoenergy and Nanosystems Chinese Academy of Sciences Liu, Zhuo; Institute of Nanoenergy and Nanosystems Chinese Academy of Sciences Li, Zhou; Institute of Nanoenergy and Nanosystems Chinese Academy of Sciences
Keywords:	Polymer, Property, Consistency, Triboelectric series, Chemical group
Speciality:	Energy Materials

SCHOLARONE™
Manuscripts

The Overlooked Key Factors for Accurate Determination of Polymer Triboelectric Series

Hongyu Meng^{1*}, Yansong Gai¹, Yuan Bai¹, Qiao Yu¹, Zhuo Liu¹ & Zhou Li^{1,2,3*}

Triboelectrification (TE), also known as contact electrification (CE), refers to the phenomenon where two materials acquire opposite charges upon contact and subsequent separation due to charge transfer [1]. The electrostatic accumulation can lead to safety hazards, equipment damage, product defects, and even health risks, making it crucial to mitigate TE in certain industrial and daily scenarios [2]. While TE also enables valuable technological applications [3], such as electrostatic precipitation, spraying, printing, filtration, separation, and contact-electro-catalysis [4]. Furthermore, in 2012, Zhong Lin Wang invented the triboelectric nanogenerator (TENG), based on coupling TE effect with electrostatic induction. The triboelectric components of TENG primarily consist of polymers. When two polymers with divergent triboelectric polarities come into contact and then separate under external forces, electrons transfer between them, generating electric current in external circuit and thereby producing electrical energy. This mechanism allows TENGs to efficiently harvest dispersed, high-entropy mechanical energy from the environment or human motion into electrical energy, demonstrating broad potential in energy harvesting, implantable or wearable electronics, the internet of things, self-powered sensing systems (Fig. 1) [4, 5]. Establishing reliable triboelectric series for polymers are essential for elucidating the fundamental mechanisms of their triboelectrification, and providing critical guidance for material selection and design to better control over triboelectric effects, such as minimize electrostatic hazards (e.g., preventing fires) or enhance electrical output for high-performance TENGs [6]. **Using the TENG output analysis enables accurate and direct quantification of transferred charge between different testing polymer films and the reference material (e.g., PTFE film) during periodic contact-separation. The triboelectric series of these polymer films can be determined by ranking the magnitudes of the transferred charge. In this method, a reliable triboelectric series requires accuracy and consistency of some physical and chemical properties for different testing polymer films, a criterion often overlooked and unmet in current triboelectric polarity studies, leading to questionable accuracy. This perspective analyzes accuracy or consistency**

challenges in triboelectric polymers (especially biodegradable polymers) films, covering purity, surface roughness, and mass/thickness, offering valuable insights for researchers and engineers engaged in triboelectric polymer research and applications.

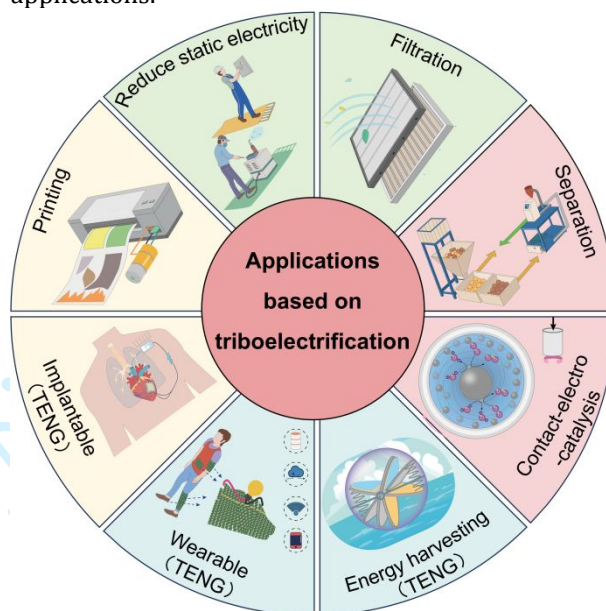


Figure 1. The applications based on triboelectrification effect, including reducing static electricity, electrostatic filtration, separation, printing, contact-electro-catalysis, and TENGs used in energy harvesting, implantable or wearable electronics.

Charge carriers in CE process can be electrons, ions, or small charged material fragments. Recent experimental evidence strongly suggests that electron transfer drove by the overlap of electron cloud during CE process plays a dominant role [4]. The triboelectric series of polymers can be established based on their relative tendencies of their triboelectric positive or negative polarity, which corresponds to their strength of electron donating (ED) or electron withdrawing (EW) ability [7, 8]. Since polymers consist of diverse chemical groups with varying ED or EW abilities, the triboelectric polarity and density of these groups

¹ Beijing Institute of Nanoenergy and Nanosystems, Chinese Academy of Sciences, Beijing 101400, China

² Tsinghua Changgung Hospital, School of Clinical Medicine, School of Biomedical Engineering, Tsinghua Medicine, Tsinghua University, Beijing 100084, China

³ School of Nanoscience and Engineering, University of Chinese Academy of Sciences, Beijing 100049, China

* Corresponding author (email: menghy@iccas.ac.cn; zli@binn.cas.cn)

fundamentally determine a polymer's triboelectric properties. Despite the first triboelectric series was established over 200 years ago, variations exist among sequences reported by different researchers [6, 9, 10]. Experimental conditions (e.g., humidity, temperature) can cause some deviations due to triboelectric series is determined experimentally [11, 12]. However, based on a comprehensive literature investigation and experimental data, we conclude that the accuracy and consistency of properties for tested polymers remains the primary factor influencing the accuracy of triboelectric series when using charge transfer measurement methods (the TENG output analysis), in which different tested polymers films are periodically contacted with and separated from the reference material (e.g., PTFE film) under the drive of linear motor, and using a digital oscilloscope and an electrometer to characterize the short-circuit charge (Fig. 2a and 2b) [6]. We observe that many studies on triboelectric polarity comparison fail to ensure uniformity in these properties [13-18], leading to questionable accuracy. This perspective mainly discusses the relationship between the consistency of properties and the accuracy of triboelectric series for polymers, especially for biodegradable polymers. The properties mentioned including the purity (Fig. 2c), surface roughness (Fig. 2d), mass or thickness (Fig. 2e) of the tested triboelectric polymers films.

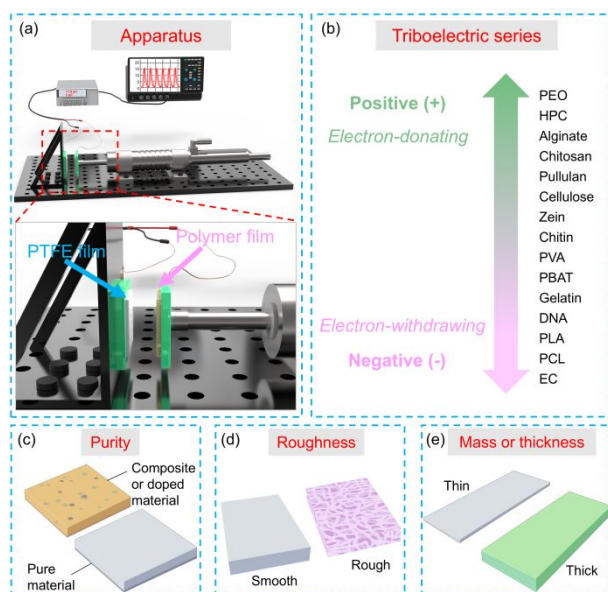


Figure 2. Consistency of polymer properties in triboelectric series experiments. (a) Apparatus for testing the triboelectric series using charge transfer measurement methods. (b) A triboelectric series of some degradable polymers reported. The inconsistency of the properties such as (c) purity, (d) surface roughness, and (e) mass or thickness for tested triboelectric polymer films leads to

questionable accuracy of their triboelectric polarities.

Consistency in purity. Sufficient purity is essential for obtaining accurate triboelectric series. During the test, polymers are prepared into thin films. However, some polymers require the addition of organic or inorganic molecules to enhance film formation or improve mechanical properties. The inclusion of these additives results in the triboelectric polarity measurements reflecting the properties of the composite films, rather than those of the pure polymers, a detail often overlooked in some reports. For instance, chitosan tends to be dissolved in acidic aqueous solutions. Consequently, the reported chitosan films inevitably retain residual acid substances (e.g., acetic acid or hydrochloric acid) unless additional acid removal steps are implemented [13, 16, 19]. Zheng et al. reported a triboelectric series (from positive to negative) as follows: glass fiber fabric, starch film, chitosan/starch composite film, chitosan film, aluminum foil [13]. However, the presence of acetic acid in the chitosan film prevents the accurate determination of chitosan's intrinsic triboelectric polarity [19]. This interference also compromises the accurate comparison of the ED abilities between amine and hydroxyl groups, due to the main difference for chitosan is that one of the hydroxyl groups is replaced by an amine group in its molecular repeating unit compared with starch. In addition, glycerol, utilized as a plasticizer, can improve the flexibility of some polymers when incorporated. Jiang et al. prepared five distinct protein composite films containing 30 wt% glycerol, and subsequently compared their triboelectric polarities with other polymers, including nylon-11, wool, PDMS, and PTFE [14]. However, the introduction of glycerol resulted in a discernible divergence in the measured triboelectric polarities of the protein composite films compared to those of pure protein films. Furthermore, another crucial factor concerns the moisture content requirements for accurate triboelectric evaluation [15]. Since different polymers possess distinct hydrophilicity, rigorous drying protocols are essential prior to testing. This is particularly critical for hygroscopic polymers evaluated under high-humidity conditions. Insufficient drying leads to measurement artifacts, where the recorded triboelectric polarity reflect those of a water-containing polymer composite film rather than the true characteristics of the pure polymer.

Consistency in surface roughness. For TENGs or triboelectric tests, a larger contact area between triboelectric polymers leads to greater charge transfer and higher electrical output [20]. Hence, to obtain accurate triboelectric series assessment, different polymer films should be prepared with identical shape and contact area, and then subjected to periodic contact-separation with the reference PTFE film.

Besides, achieving similar surface roughness across samples is crucial for obtaining reliable triboelectric series, because disparities in surface roughness leads to variations in their actual or effective contact areas with the PTFE film, even when their macroscopic areas are identical. Regrettably, some research neglect to account for the impact of surface roughness inconsistencies. For instance, when comparing the triboelectric positive polarity of porous cellulose and chitosan aerogel film, differences in specific surface area (surface roughness) result in unequal effective contact areas. This inconsistency may introduce errors in assessing the true triboelectric series of chitosan and cellulose, as well as in quantifying the contributions of amine and hydroxyl groups to positive ability [16]. Another study compared the triboelectric series of PLGA, chitin, PLA, copy paper, rice paper, and silk film. Despite the standardization of film area and thickness across all samples, PLGA and PLA were synthesized via solution-drying, whereas copy paper, rice paper, and silk films were utilized as received, without further processing. These disparate fabrication methods inevitably introduce variations in surface roughness (and thus effective contact area), potentially compromising the accuracy of their triboelectric series [17].

Consistency in mass or thickness. Theoretically, the triboelectric polarity of polymers is determined by their inherent ED or EW ability, independent of their mass or thickness. However, for the testing of triboelectric series, consistency in the mass or thickness is essential, because the tested polymer films and the reference polymer (PTFE) can function as a pair of triboelectric materials of a TENG, and extensive studies have demonstrated that variations in thickness of triboelectric films significantly influence the amount of transferred charge of TENGs [20]. For most biodegradable polymers, composed primarily of C, H, O, or C, H, O, N elements, the density is relatively uniform, typically around 1.2-1.3 g/cm³ [10, 21]. Given this similarity in density, maintaining uniform mass across different polymer films inherently ensures comparable thickness. Therefore, when dealing with these polymers, standardization in film mass or thickness is crucial to ensure the accuracy of triboelectric series and the proper evaluation of relative ED or EW tendencies of the chemical groups. However, this aspect has not received widespread attention. For instance, the triboelectric series of polyesters [10, 22], such as polylactic acid (PLA), poly (butylene succinate) (PBS), and polycaprolactone (PCL), varies across different studies [6, 18]. The three polyesters share similar molecular structure, consisting of repeating alkane segments and ester groups. The key structure distinction lies in the density of ester groups along the backbone: PLA features one ester group per 2 carbon atoms in the

main chain, PBS has one per 4, and PCL has one per 6. Standardization of film mass (or thickness) during triboelectric testing would establish a well-defined quantitative relationship between ester (or alkane) group density and their relative triboelectric polarities [6]. This controlled experimental approach would not only clarify the relative ED or EW abilities of these polyesters, but also provide more reliable insights into how specific chemical group density influences performance, thereby resolving current inconsistencies in reported data. Furthermore, when ranking more kinds of polymers, consistent films mass or thickness can also significantly improve the accuracy in analyzing the relative triboelectric polarity or ED or EW abilities of both the polymers and their groups [6].

In conclusion, the accuracy and reproducibility of triboelectric series have long been key concerns in scientific research. The relative triboelectric polarities of polymers are fundamentally determined by the types and density of their chemical groups exhibiting varying ED or EW abilities. We conclude that the accuracy and consistency of properties, including material purity, surface roughness, and mass (or thickness) for tested polymer films is crucial for establishing reliable triboelectric series. Establishing reliable triboelectric series are essential for elucidating the fundamental mechanisms of their triboelectrification, and providing critical guidance for material selection and design to better control over triboelectric effects.

15; accepted xxx 2015;
Published online xxx 2024

- 1 Wang ZL, Wang AC. On the origin of contact-electrification. *Materials Today*, 2019, 30: 34-51
- 2 Bhattacharjee P. Electrostatic discharge hazards and control measures. City: IEEE, Year: 1-3
- 3 Castle GP. A century of development in applied electrostatics [history]. *IEEE Industry Applications Magazine*, 2010, 16(4): 8-13
- 4 Wang Z, Dong X, Tang W, et al. Contact-electro-catalysis (cec). *Chemical Society Reviews*, 2024,
- 5 Wang ZL. From contact electrification to triboelectric nanogenerators. *Reports on Progress in Physics*, 2021, 84(9): 096502
- 6 Meng H, Yu Q, Liu Z, et al. Triboelectric performances of biodegradable polymers. *Matter*, 2023, 6(12): 4274-4290
- 7 Li S, Nie J, Shi Y, et al. Contributions of different functional groups to contact electrification of polymers. *Advanced Materials*, 2020, 32(25): 2001307
- 8 Zhang R, Olin H. Material choices for triboelectric nanogenerators: A critical review. *EcoMat*, 2020, 2(4): e12062
- 9 Zou H, Zhang Y, Guo L, et al. Quantifying the triboelectric series. *Nature communications*, 2019, 10(1): 1427
- 10 Żenkiewicz M, Żuk T, Markiewicz E. Triboelectric series and electrostatic separation of some biopolymers. *Polymer Testing*, 2015, 42: 192-198
- 11 Zheng X, Zhang R, Huang H. Theoretical modeling of relative humidity on contact electrification of sand particles. *Scientific Reports*, 2014, 4(1): 4399
- 12 Xu C, Wang AC, Zou H, et al. Raising the working temperature of

- a triboelectric nanogenerator by quenching down electron thermionic emission in contact - electrification. *Advanced Materials*, 2018, 30(38): 1803968
- 13 Zheng Z, Yu D, Wang B, et al. Ultrahigh sensitive, eco-friendly, transparent triboelectric nanogenerator for monitoring human motion and vehicle movement. *Chemical Engineering Journal*, 2022, 446: 137393
 - 14 Jiang C, Zhang Q, He C, et al. Plant-protein-enabled biodegradable triboelectric nanogenerator for sustainable agriculture. *Fundamental Research*, 2022, 2(6): 974-984
 - 15 Zhang J, Boyer C, Zhang Y. Enhancing the humidity resistance of triboelectric nanogenerators: A review. *Small*, 2024, 20(36): 2401846
 - 16 Zheng Q, Fang L, Guo H, et al. Highly porous polymer aerogel film - based triboelectric nanogenerators. *Advanced Functional Materials*, 2018, 28(13): 1706365
 - 17 Chen G, Xu L, Zhang P, et al. Seawater degradable triboelectric nanogenerators for blue energy. *Advanced Materials Technologies*, 2020, 5(9): 2000455
 - 18 Wu Y, Luo Y, Qu J, et al. Nanogap and environmentally stable triboelectric nanogenerators based on surface self-modified sustainable films. *ACS Applied Materials & Interfaces*, 2020, 12(49): 55444-55452
 - 19 Wang R, Gao S, Yang Z, et al. Engineered and laser - processed chitosan biopolymers for sustainable and biodegradable triboelectric power generation. *Advanced Materials*, 2018, 30(11): 1706267
 - 20 Hasan S, Kouzani AZ, Adams S, et al. Comparative study on the contact-separation mode triboelectric nanogenerator. *Journal of electrostatics*, 2022, 116: 103685
 - 21 Samir A, Ashour FH, Hakim AA, et al. Recent advances in biodegradable polymers for sustainable applications. *Npj Materials Degradation*, 2022, 6(1): 68
 - 22 Zheng Q, Zou Y, Zhang Y, et al. Biodegradable triboelectric nanogenerator as a life-time designed implantable power source. *Science advances*, 2016, 2(3): e1501478

Acknowledgements This work was financially supported by National Key Research and Development Program of China (2022YFB3804700), National Natural Science Foundation of China (T2125003, 52203325), Beijing Natural Science Foundation (L245015, Z240022), Shanghai "science and technology innovation action plan" experimental animal research project (22140902000), and the Fundamental Research Funds for the Central Universities.

Author contributions Meng HY proposed the ideas and wrote the draft; Gai YS, Bai Y, Yu Q and Liu Z performed formal analysis and visualization; Li Z leaded and reviewed this work. All authors contributed to the general discussion.

Conflict of interest The authors declare that they have no conflict of interest.



Hongyu Meng is an assistant professor at Beijing Institute of Nanoenergy and Nanosystems, Chinese Academy of Sciences. He obtained his Ph.D. from Institute of Chemistry, Chinese Academy of

Sciences in 2019. His research focuses on biodegradable electronic devices and bio-composite materials, including triboelectric and piezoelectric materials.




Zhou Li is currently a professor at Beijing Institute of Nanoenergy and Nanosystems, Chinese Academy of Sciences. He received his Ph.D. from Peking University in Department of Biomedical Engineering in 2010, and Bachelor's Degree from Wuhan University in 2004. He joined School of Biological Science and Medical Engineering of Beihang University in 2010 as an Associate Professor. His research interests include nanogenerators, in vivo energy harvesters, self-powered medical devices, and biosensors.


精确测定高分子摩擦电序中被忽视的关键因素

孟宏宇^{1*}, 盖延松¹, 白源¹, 于巧¹, 刘卓¹, 李舟^{1,2,3*}


研究和比较高分子的摩擦起电性能, 并建立准确的高分子摩擦电序, 不仅有助于研究人员深入认识其摩擦起电的潜在机理, 而且对于通过合理选择或设计摩擦电高分子来更加可控调节摩擦起电效应具有重要意义。建立准确的摩擦电序的必要条件是高分子理化性能的准确性和一致性, 而在很多相关研究中被忽视, 导致报道的摩擦电序的准确性有待进一步探讨。本论文通过对摩擦电序测试中所研究的摩擦电高分子材料, 尤其可降解高分子材料的理化性能一致性对摩擦电序准确性的影响进行探讨, 包括材料纯度、表面粗糙度、质量(或厚度)的一致性等方面。本论文有望对从事高分子摩擦电研究及相关应用方面的研究人员提供有益参考。

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

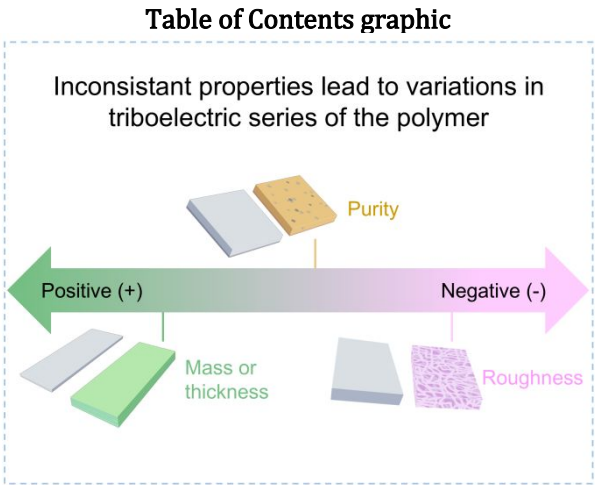


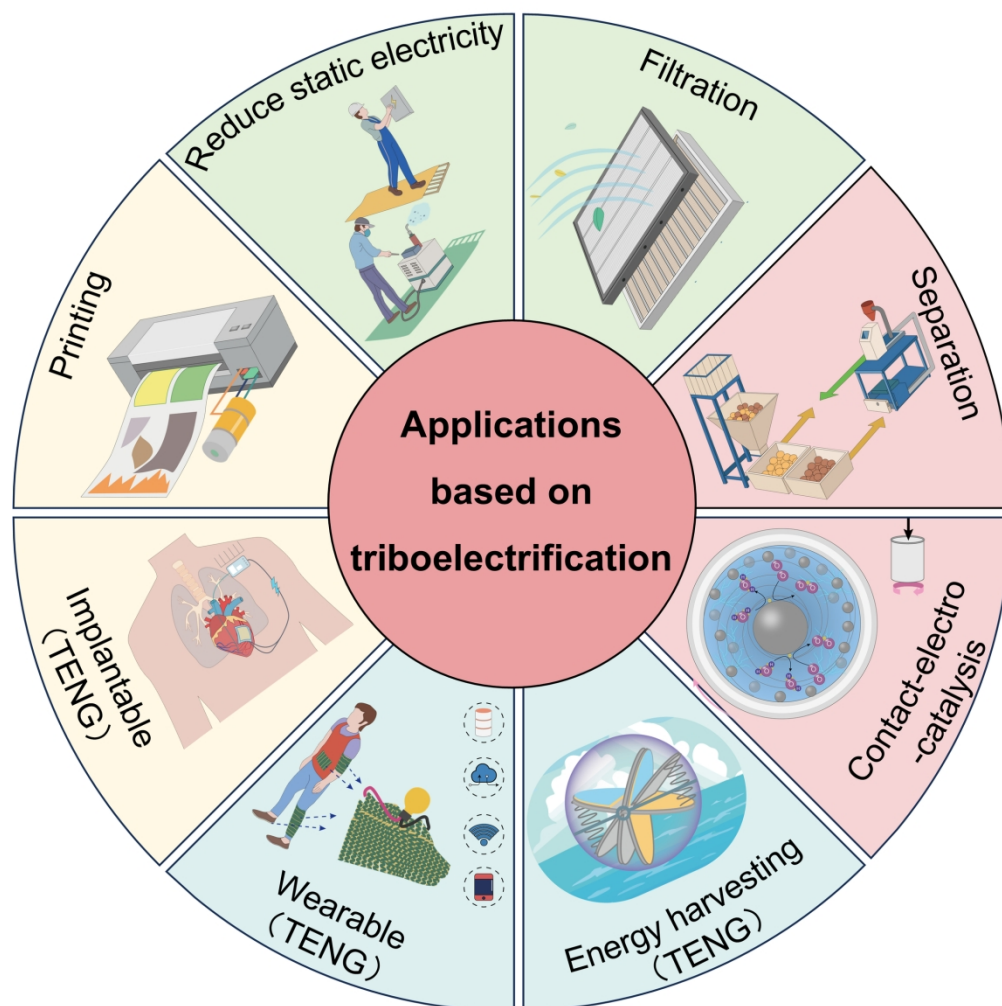

190x193mm (300 x 300 DPI)

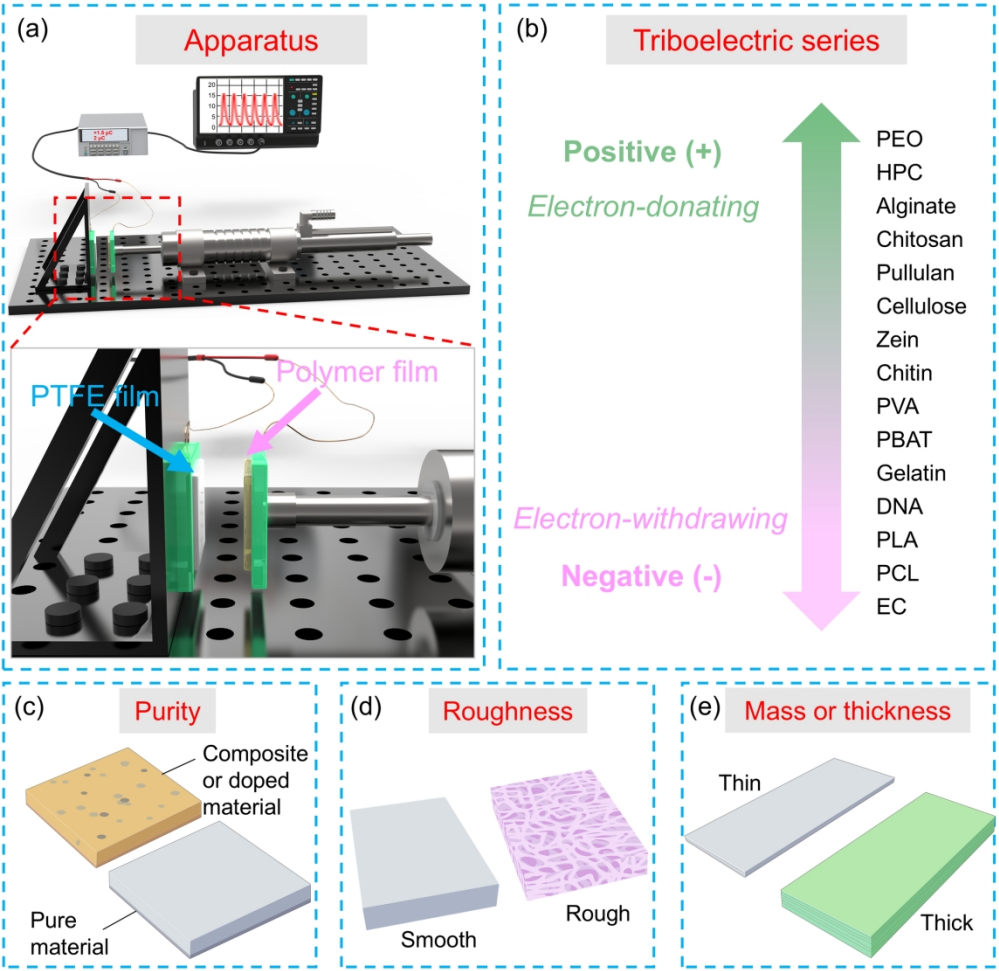

190x185mm (300 x 300 DPI)

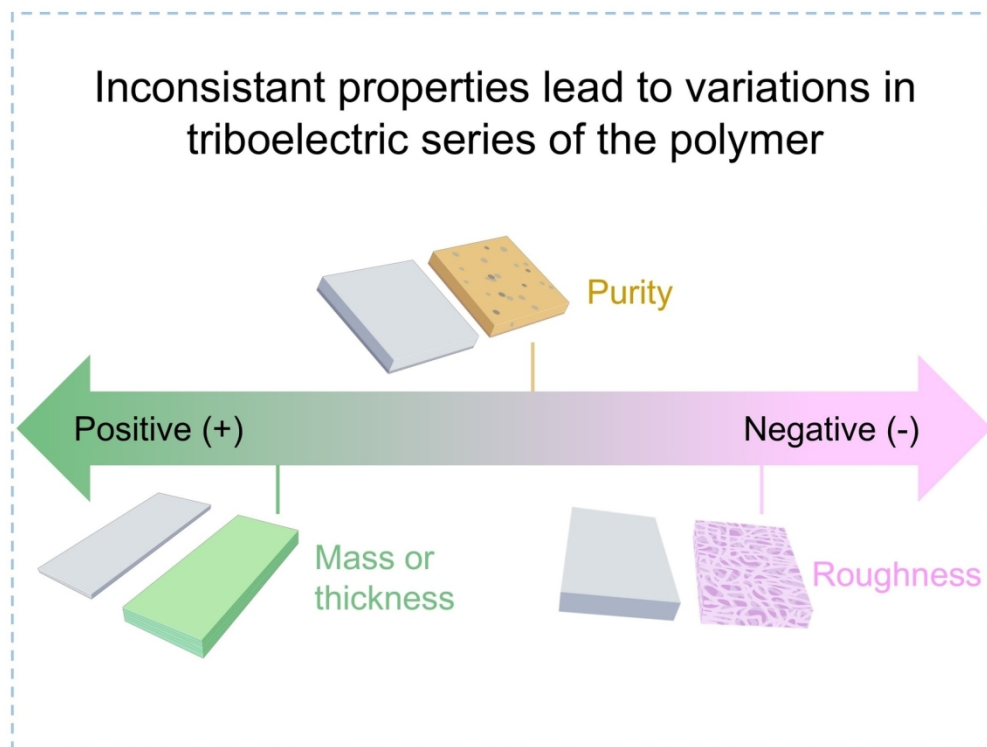

146x110mm (300 x 300 DPI)